



Review of the main parameters for the development of antifouling supports

Jamile de Melo Carvalho^{1}, Lilian Lefol Nani Guarieiro²
1 SENAI CIMATEC University, Oil and Gas, Salvador, Bahia, Brazil*

**Corresponding author: SENAI CIMATEC University; Salvador, Brazil 41650-010; jamile.carvalho@fbter.org.br*

Abstract: Marine biofouling is the process by which organisms such as barnacles, mollusks, algae, and corals attach themselves to submerged surfaces, compromising the performance of structures such as ship hulls, sensors, and pipes. This accumulation increases hydrodynamic resistance, raises fuel consumption, and favors the spread of invasive species. To mitigate these effects, anti-fouling coatings began to be used, initially formulated with highly toxic biocides such as tributyltin (TBT) and triphenyltin (TPT). However, due to the prolonged environmental impacts of these compounds, their use was banned. Given this scenario, alternatives based on natural compounds, polymers, bio-inspired surfaces, and nanoparticles have emerged. This study aimed to conduct a systematic review of the literature to identify the main parameters involved in the development of anti-fouling coatings applied in marine environments. The search was conducted in the ScienceDirect, Scopus, Web of Science, PubMed, and SciELO databases, using the keyword “antifouling,” with no time restriction. Approaches regarding material types, physicochemical properties, evaluation methods, and technical gaps were analyzed. VOSviewer software was used to map trends through keyword analysis. The results indicated a significant growth in publications from 2020 onwards, with contributions from China, the United States, and Brazil standing out. The review identified technological approaches, as well as testing standards that seek to ensure effectiveness, durability, and environmental safety. Despite advances, challenges such as field validation and the long-term durability of coatings remain significant obstacles.

Keywords: marine biofouling, antifouling, coating, biocides

1. Introduction

Marine biofouling is a natural process in which organisms such as barnacles, mollusks, corals, mussels, and algae attach themselves to submerged surfaces, such as ship hulls, industrial structures, filtration membranes, and sensors, compromising their performance and integrity (1). The accumulation of these organisms increases hydrodynamic resistance, raises fuel consumption, and intensifies carbon emissions, in addition to favoring the spread of invasive species (2). In structures such as pipes and sensors, biofouling reduces efficiency, increases maintenance frequency, and shortens the useful life of surfaces (3). Conventional anti-fouling coatings have made extensive use of highly toxic biocides, such as tributyltin (TBT), widely recognized as the most effective compound ever developed for this purpose. However, its serious

environmental impacts, including toxicity to marine organisms, led to its total ban in 2008 by the International Maritime Organization (IMO) (4). Considering the environmental damage associated with the use of toxic compounds in anti-fouling coatings, it is essential to develop solutions that are truly non-toxic and environmentally safe. To achieve this goal, it is essential to adopt multidisciplinary approaches that integrate knowledge of chemistry and physics, whose interactions contribute to the development of more effective anti-fouling strategies. The objective of this study was to conduct a systematic review of the literature focusing on the main parameters involved in the development of anti-fouling supports with low environmental impact applied to marine environments. The study sought to identify technological trends, characteristics of the materials used, and challenges faced, based on



the analysis of scientific publications and keyword mapping performed with VOSviewer software.


2. Methodology

A systematic review of the literature was conducted to identify and analyze the main scientific advances in the development of antifouling coatings applicable to marine environments. Searches were performed on ScienceDirect, Scopus, Web of Science, PubMed, and SciELO platforms using the descriptor “antifouling” without time restrictions, with the aim of providing a comprehensive and up-to-date overview of the topic. Specific criteria were applied to refine the results: there was no language restriction, and only complete scientific articles with an experimental approach were considered. In addition, priority was given to studies available in open access and presenting technical data, such as type of material, physical-chemical and mechanical properties, exposure time, evaluation methods, and performance results under laboratory and/or field conditions. After the initial screening, 32 articles met the selection criteria and were included in the detailed analysis. The final choice was based on a qualitative analysis, considering the main technical highlights, such as the parameters evaluated and the experimental methods used. The evaluation of the data extracted from the articles was conducted with the support of Microsoft Excel, used for data organization and

analysis, and VOSviewer, used for keyword mapping from the Web of Science database, which allowed conceptual connections between studies and the detection of recent advances related to the development of approaches that minimize environmental damage in the control of biofouling.


3. Results and Discussions

The analysis was qualitative in nature and resulted in the selection of 32 articles. Figure 1 shows the temporal evolution of publications on anti-fouling coatings, based on the analysis of the selected scientific articles. There was limited production between 2010 and 2020, with few papers published during this period, marked by initial approaches focused on natural extracts (5–7). From 2021 onwards, there has been a steady stream of academic production, driven by the search for alternatives to conventional biocides and the advancement of analytical tools, such as X-ray fluorescence spectroscopy (XRF) (8) and computational modeling applied to coating performance (1). Research has focused on superhydrophobic surfaces (9,10), bio-inspired coatings (11,12), with emphasis on the use of functional nanoparticles and the development of biocides with low environmental impact (13–16), in addition to previous studies focused on conventional systems with controlled release of metal ions, especially copper-based ones (8). Currently, there is a continuous growth in the number of publications, reflecting the increase in interest and scientific production, with an



emphasis on innovative biomaterials and nanotechnological approaches (17,18). Recent trends point to the consolidation of technologies such as zwitterionic polymers (19,20) and multifunctional nanostructures (21), in addition to the growing demand for long-term studies and comprehensive ecological assessments of new anti-fouling materials.

Graph 1 – Annual distribution of scientific publications on antifouling coatings.

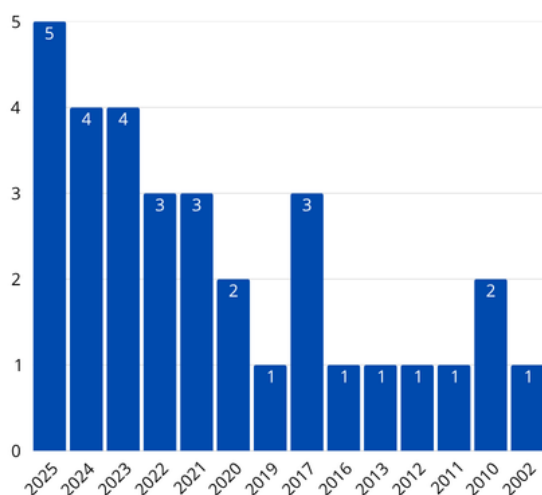


Source: Data compiled by the author (2025)

The mapping of scientific production by country, shown in Graph 2, highlights China's leadership, especially in studies involving nanomaterials (such as cuprous oxide and silica) and surface modification techniques, such as controlled roughness (10,15,17). Europe is represented by Italy, which stands out in the development of advanced polymers (22), while Sweden focuses its efforts on analytical methods and reducing environmental impacts (14). Despite its vast marine biodiversity, Brazil still invests little in


research aimed at developing non-toxic anti-fouling agents. This is still an innovative area in the country, with few research groups dedicated to the topic (5–7). In terms of technological trends, Asian countries such as China, Korea, and Japan lead in the synthesis of new materials, while Europe and the United States prioritize practical applications, such as the use of sensors and field tests (12). It is worth noting that in three articles, it was not possible to identify the country of origin of the research.

Graph 2 – Countries with the highest scientific output on antifouling coatings.

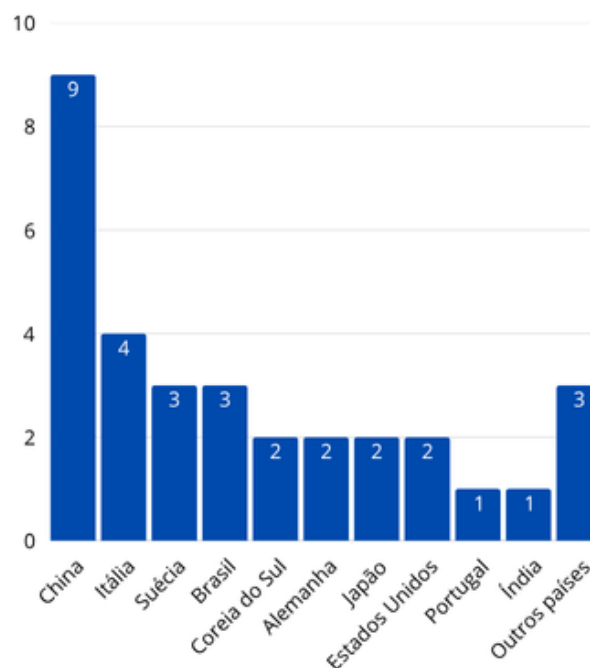


Source: Data compiled by the author (2025)

The analysis of the most frequent keywords in the articles, presented in Graph 3, reinforces the predominant focus on the terms “antifouling” and “biofouling,” which are the most frequent in



research on antifouling coatings, reflecting the central focus of the area. Technological approaches such as nanoparticles (15,16), superhydrophobic surfaces (9,10), and controlled release (18) also stand out, indicating a trend toward effective solutions with low environmental impact. Terms such as “field tests” and “non-toxic biocides” (5,23,24,33), although less frequently cited, point to important gaps in practical validation and environmental safety. Figure 3 shows a transition from traditional methods to innovative and bio-inspired strategies.

Graph 3 - Most frequent keywords in studies on antifouling coatings.


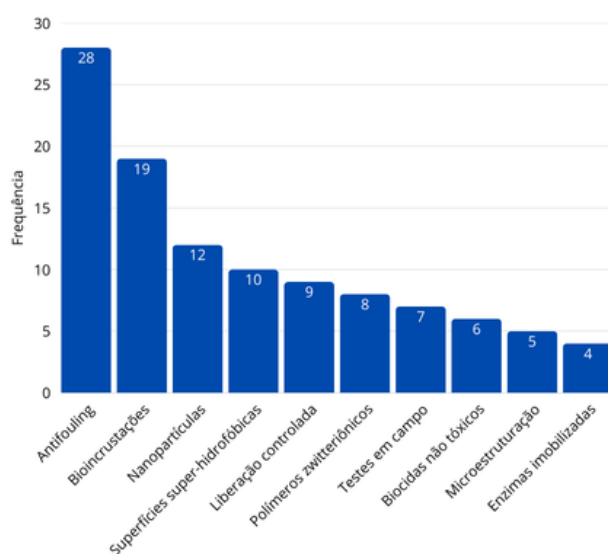


Source: Data compiled by the author (2025).

The systematic review was expanded with the use of keyword mapping through VOSviewer, using 5,647 records from Web of Science with the word “antifouling” in the title.

In Image 01, the graph shows four main clusters. The first, represented by the color green, focuses on studies related to coating technologies and the performance of materials applied to marine environments, highlighting terms such as “antifouling coating,” “fouling release coatings,” and “performance.” The red cluster brings together research on colonization mechanisms and the challenges caused by biofouling, with an emphasis on keywords such as “biofouling,” “adhesion,” “settlement,” and “toxicity.” The blue cluster addresses investigations into interactions at the molecular level, including terms such as “surfaces,” “protein adsorption,” and “poly (ethylene glycol).” The yellow cluster integrates works that explore chemical composition, protein behavior, and material behavior in improving antifouling performance. The term “adhesion” stood out as the link between the biological and innovation areas in coatings, while “nanoparticles” presented more limited connections, indicating potential gaps to be explored. Overall, the results show that, although there have been significant advances in the practical effectiveness of antifouling agents, there is still a need for innovation to address biofouling.

Image 01 – Keyword mapping in VOSviewer, highlighting four main clusters.

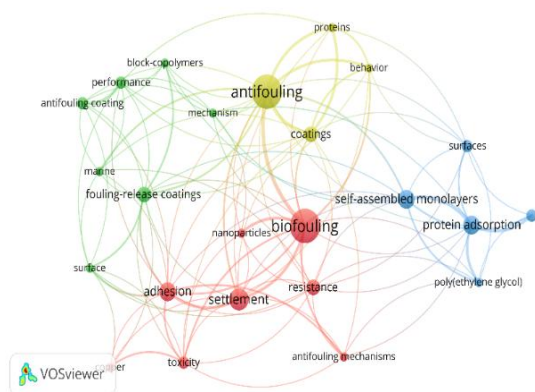

Source: Data compiled by the author (2025)

Table 1 highlights the advancement and complexity of anti-fouling technologies, showing a critical balance between effectiveness and environmental responsibility. Biocidal coatings (8,14–16) remain effective but raise concerns about ecotoxicity. Alternatively, solutions based on natural bioactives (7,9,24,25) offer lower environmental impact but have reduced durability. Physical technologies, such as superhydrophobic (9,10,12) and micro/nanotextured (17,26,27) surfaces, stand out for their durability and absence of toxic compounds, making them particularly suitable for offshore structures that are difficult to maintain.


Table 1 - Comparison of the main antifouling coatings in terms of mechanism of action, durability, removal, and applications.

Type	Mechanism of Action	Shelf Life	Removal	Applications	Ref.
Biocides	Controlled release of toxic ions (Cu, Zn) or organic compounds (capsaicin).	1–5 years (depending on release rate)	Natural degradation or mechanical cleaning.	Ship hulls, port structures.	(8,13–16)

Physical (Micro/Nanotextured)	Creation of rough/irregular surfaces to reduce larval adhesion.	2–10 years (high durability)	Abrasion resistant.	Marine sensors, pipes.	(17,26,27,29)
Hydrophobic	Reduced wettability to hinder organism attachment.	1–3 years (limited by chemical degradation).	Cleaning with water jets or solvents.	Submerged equipment, aquaculture.	(9,10,21)
Superhydrophobic	Combines extreme hydrophobicity and microstructures (contact angle >150°). e microestruturas (ângulo de contato >150°).	3–8 years (high resistance).	Self-cleaning (lotus effect).	Offshore wind energy, aquatic drones.	(9,10,12)
Polymers (Zwitterionic/Hydrogels)	Neutral surface charge and hydration to repel biofilms.	6 months – 2 years (renewable).	Degradation or recoating	Membranes, medical implants.	(19–22,30)
Natural Bioactive Compounds	Release of extracts/enzymes that inhibit larval settlement.	6 months – 3 years (depending on stability).	Biodegradation.	Marine protected areas, sustainable aquaculture.	(5,7,22,24,31)
Hybrids	Combines multiple mechanisms (e.g., biocide + texture).	2–7 years (synergy).	Varies depending on components.	Critical applications (petroleum, defense).	(13,18,20)

Source: Data compiled by the author (2025)

However, Table 1 also highlights the lack of standardization in validation criteria. The variation in testing methods, ranging from field tests (5,28) to projections based on laboratory data (26), makes it difficult to compare the results obtained between different technologies. In this



context, hybrid systems (13,18,20) stand out for integrating different mechanisms (physical, chemical, biological), achieving synergy in performance, durability, and functionality. The analysis reinforces that future developments should prioritize technologies with lower environmental impact, greater durability, and standardized validation, with hybrid systems emerging as a promising solution for critical environments, such as offshore platforms and oil industry structures.

Table 2 presents the main technical parameters of antifouling coatings, highlighting criteria such as thickness, adhesion, durability, environmental resistance, and effectiveness. Thin coatings, such as PDMS (27), are ideal for sensors, while thick coatings, such as thermoplastics (26), are suitable for robust structures. Hydrogels and zwitterionic polymers (19–21, 30) showed good adhesion, and durability ranged from 6 months to 10 years, with textured surfaces standing out (27). In terms of environmental resistance, coatings with amorphous Fe (11) and PDMS (10) stood out, while materials such as capsaicin (18) showed lower stability. Antifouling efficacy was high on superhydrophobic surfaces (9), PDMS (10), chitosan (17), and enzymes (22). Challenges remain, such as the lack of standardization of tests and the scarcity of long-term validations. Recommended solutions include combined methodologies, such as XRF with bioassays (14), as well as hybrid criteria.


Table 2. Technical parameters and validation methods for anti-fouling coatings

Parameter	Range/Description	Validation Methods	Representative Articles (No.)
Thickness	20–500 µm	-	(10,17,19,21,26,27,30)
		Profilometry - Electron microscopy	
Adhesion	- Zwitterionic polymers/hydrogels: Excellent	Lab: ASTM D3359 (cross-cut), pull-off	(9,10,19–21,26,30)
	- Hydrophobic surfaces: Average	Field: Exposure to waves/currents	
Durability	6 months–10 years	Lab: Accelerated aging (UV/saline)	(10,12,14,26–28)
		Field: Monitoring (6–24 months)	
UV/Saltwater Resistance	High: PDMS, Amorphous Fe	Lab: UV/Saline Chambers (ASTM G154)	(10,11,13,19,22,30)
	Medium/Low: Hydrogels, enzymes	Field: Exposure in coastal areas	
Antifouling efficacy	70–99% inhibition	Lab: Bioassays (larvae/biofilms)	(1,13,14,17,22,24,28,32)
		Field: Natural colonization (6–12 months)	
Combined Methods	XRF + ecotoxicology	Example: XRF laboratory + field	(1,8,14,27)
	- Microstructuring + bioassays		

Source: Data compiled by the author (2025).

4. Conclusion

Marine biofouling represents a significant technical and environmental challenge, especially in submerged structures, where it compromises functional performance, increases operating costs, and exacerbates ecological impacts. The systematic review carried out allowed us to map the main advances in the development of anti-fouling coatings with less environmental impact.



There has been a significant shift from the use of toxic biocides to bio-inspired solutions, driven by the negative impacts of conventional substances, such as toxicity to non-target organisms, bioaccumulation, and ecological imbalance in the marine environment. The analysis of the tables showed technological diversity, with emphasis on superhydrophobic surfaces, zwitterionic polymers, hydrogels, and hybrid systems, which have shown promise due to their high anti-fouling effectiveness. However, important challenges remain, such as the absence of standardized evaluation protocols, the scarcity of long-term studies, and the production limitations of some emerging technologies.


5. References

- [1] 1. She W, Wang H, Linardi D, Chik SY, Lan Y, Chen F, et al. Mode of action of antifouling compound albobungin in inhibiting barnacle larval settlement. *iScience* [Internet]. 2023 Jul 21 [cited 2025 Jul 22];26(7):106981. Available from: <https://www.cell.com/action/showFullText?pii=S2589004223010581>
- [2] 2. Morgan RN, Ali A AI, Alshahrani MY, Aboshanab KM. New Insights on Biological Activities, Chemical Compositions, and Classifications of Marine Actinomycetes Antifouling Agents. *Microorganisms* [Internet]. 2023 Oct 1 [cited 2025 Jul 5];11(10):2444. Available from: <https://www.mdpi.com/2076-2607/11/10/2444/htm>
- [3] 3. Wang J, Li L, Wu Y, Liu Y. Design and Application of Antifouling Bio-Coatings. *Polymers* 2025, Vol 17, Page 793 [Internet]. 2025 Mar 17 [cited 2025 Jul 22];17(6):793. Available from: <https://www.mdpi.com/2073-4360/17/6/793/htm>
- [4] 4. Cognetti G, Maltagliati F, Pretti C. Antifouling coatings and ecological control in marinas. *Mar Pollut Bull* [Internet]. 2012 Feb 1 [cited 2025 Jul 5];64(2):175–6. Available from: <https://www.sciencedirect.com/science/article/pii/S0025326X11005546?via%3Dihub>
- [5] 5. Pereira RC, Carvalho AGV, Gama BAP, Coutinho R. Field experimental evaluation of secondary metabolites from marine invertebrates as antifoulants. *Brazilian Journal of Biology* [Internet]. 2002 [cited 2025 Jul 22];62(2):311–20. Available from: <https://www.scielo.br/j/bjb/a/gddmrcmdvfn5mz8R58wqgQ/?lang=en>
- [6] 6. Cuadrado-Silva CT, Castellanos-Hernández L, Osorno-Reyes OE, Ramos Rodríguez FA, Duque Beltrán C, Puyana-Hegedus M. Estudio químico y evaluación de la actividad antifouling del octocoral caribeño *Eunicea laciniata*. *Quim Nova* [Internet]. 2010 [cited 2025 Jul 22];33(3):656–61. Available from: <https://www.scielo.br/j/qn/a/chTnCd8pjQX7NdLr3fxPHR/?lang=es>
- [7] 7. Ribeiro SM, Rogers R, Rubem AC, Da GB, Muricy G, Pereira RC. Antifouling activity of twelve demosponges from Brazil. *Brazilian Journal of Biology* [Internet]. 2013 [cited 2025 Jul 22];73(3):501–6. Available from: <https://www.scielo.br/j/bjb/a/8kKXVknDYhSpdCGXVfddQfb/?lang=en>
- [8] 8. Lagerström M, Ytreberg E. Quantification of Cu and Zn in antifouling paint films by XRF. *Talanta* [Internet]. 2021 Feb 1 [cited 2025 Jul 22];223:121820. Available from: <https://www.sciencedirect.com/science/article/pii/S003991402031115?via%3Dihub>
- [9] 9. Bae S, Lee YJ, Kim MK, Kwak Y, Choi CH, Kim DG. Antifouling Effects of Superhydrophobic Coating on Sessile Marine Invertebrates. *Int J Environ Res Public Health* [Internet]. 2022 Jul 1 [cited 2025 Jul 22];19(13):7973. Available from: <https://www.mdpi.com/1660-4601/19/13/7973/htm>
- [10] 10. He Z, Yang X, Mu L, Wang N, Lan X. A versatile “3M” methodology to obtain superhydrophobic PDMS-based materials for antifouling applications. *Front Bioeng Biotechnol*. 2022 Aug 29;10:998852.
- [11] 11. Li Y, Zhang LY, Zhang C, Zhang ZR, Liu L. Bioinspired antifouling Fe-based amorphous coating via killing-resisting dual surface modifications. *Sci Rep* [Internet]. 2022 Dec 1 [cited 2025 Jul 22];12(1):1–10. Available from: <https://www.nature.com/articles/s41598-021-04746-y>
- [12] 12. Doyle C, Ahmed M. Antifouling Coatings Inspired by Biological Templates. *Macromol Rapid Commun* [Internet]. 2025 Jun 1 [cited 2025 Jul 5];46(12):2400932. Available from: <https://doi/pdf/10.1002/marc.202400932>
- [13] 13. Alfieri ML, Gonçalves C, R. Almeida J, Correia-da-Silva M, Panzella L, Napolitano A. Sulfated phenolic polymers as non-toxic antifouling agents. *Eur Polym J* [Internet]. 2024 Mar 25 [cited 2025 Jul 23];208:112855. Available from: <https://www.sciencedirect.com/science/article/pii/S0014305724001162>
- [14] 14. Lagerström M, Butschle M, Larsson AI, Cachot J, Dam-Johansen K, Schackmann M, et al. Investigation of critical copper release rates for dose optimization of antifouling coatings. *Prog Org Coat* [Internet]. 2025 Jan 1 [cited 2025 Jul 22];198:108928. Available from: <https://www.sciencedirect.com/science/article/pii/S0300944024007203?via%3Dihub>
- [15] 15. Shi WZ, Liang YS, Lu B, Chen M, Li Y, Yang Z. CUPROUS OXIDE NANOPARTICLES: PREPARATION AND EVALUATION OF ANTIFOULING ACTIVITY. *Quim Nova* [Internet]. 2019 [cited 2025 Jul 22];42(6):638–41. Available from: <https://dx.doi.org/10.21577/0100-4042.20170374>
- [16] 16. Tados HRZ, Hamdona SK, El-Saharty AA, Moawad MN. Antifouling painting formulations containing green synthesized copper oxide nanoparticles using water extract of *Ulva fasciata*. *Egypt J Aquat Res* [Internet]. 2023 Mar 1 [cited 2025 Jul 22];49(1):17–22. Available from: <https://www.sciencedirect.com/science/article/pii/S1687428522000644?via%3Dihub>
- [17] 17. Yu D, Zhao X, Amores AP, Wang Y, Dutta J, Yang JL, et al. Chitosan coatings with modulated surface roughness for the inhibition of marine macrofouling. *Int J Biol Macromol* [Internet]. 2025 Jun 1 [cited 2025 Jul 22];316:144713. Available from: <https://www.sciencedirect.com/science/article/pii/S0141813025052651?via%3Dihub>
- [18] 18. Feng K, Li S, AlMasoud N, Li J, Ma Y, Yin C, et al. Nature-inspired silicone-polythiourethane coatings based on capsaicin analogue for marine biofouling control. *Chemical Engineering Journal* [Internet]. 2025 Aug 15 [cited 2025 Jul 23];518:164362. Available from: <https://www.sciencedirect.com/science/article/pii/S1385894725051976?via%3Dihub>
- [19] 19. Wu C, Zheng J, Hu J. Novel antifouling polysulfone matrix membrane modified with zwitterionic polymer. *Journal of Saudi Chemical Society* [Internet]. 2021 Aug 1 [cited 2025 Jul 22];25(8):101281. Available from: <https://www.sciencedirect.com/science/article/pii/S1319610321000867?via%3Dihub>
- [20] 20. Murali S, Agirre A, Arrizabalaga J, Rafaniello I, Schäfer T, Tomovska R. Zwitterionic stabilized water-borne polymer colloids for antifouling coatings. *React Funct Polym* [Internet]. 2024 Mar 1 [cited 2025 Jul 23];196:105843. Available from:

ISSN: 2357-7592

XI INTERNATIONAL SYMPOSIUM ON INNOVATION AND TECHNOLOGY

Quantum Technologies: The information revolution that will change the future - 2025



- <https://www.sciencedirect.com/science/article/pii/S138151482400018X>
- [21] 21. Li G, Shang L, Li D, Huang Y, Long S, Li X. Construction of silane-modified polyampholyte hydrogel coatings for multi-scale antibiofouling. *Polym Test* [Internet]. 2025 Jul 1 [cited 2025 Jul 22];148:108844. Available from: <https://www.sciencedirect.com/science/article/pii/S0142941825001588?via%3Dihub>
- [22] 22. Zaroni M, Habimana O, Amadio J, Casey E. Antifouling activity of enzyme-functionalized silica nanobeads. *Biotechnol Bioeng* [Internet]. 2016 Mar 1 [cited 2025 Jul 22];113(3):501–12. Available from: [doi/pdf/10.1002/bit.25835](https://doi.org/10.1002/bit.25835)
- [23] 23. Magin CM, Cooper SP, Brennan AB. Non-toxic antifouling strategies. *Materials Today* [Internet]. 2010 Apr 1 [cited 2025 Jul 5];13(4):36–44. Available from: <https://www.sciencedirect.com/science/article/pii/S1369702110700584?via%3Dihub>
- [24] 24. Vista de Antifouling activity of marine bacterial extracts: A non-toxic alternative as biocide [Internet]. [cited 2025 Jul 23]. Available from: <https://revistas.uv.cl/index.php/rbmo/article/view/4456/4202>
- [25] 25. Almeida JR, Correia-Da-Silva M, Sousa E, Antunes J, Pinto M, Vasconcelos V, et al. Antifouling potential of Nature-inspired sulfated compounds. *Scientific Reports* 2017 7:1 [Internet]. 2017 Feb 13 [cited 2025 Jul 22];7(1):1–11. Available from: <https://www.nature.com/articles/srep42424>
- [26] 26. Bus T, Dale ML, Reynolds KJ, Bastiaansen CWM. Thermoplastic, rubber-like marine antifouling coatings with microstructures via mechanical embossing. *Biofouling* [Internet]. 2020 Feb 7 [cited 2025 Jul 22];36(2):138–45. Available from: <https://www.tandfonline.com/doi/pdf/10.1080/08927014.2020.1734576>
- [27] 27. Cholkar A, McCann R, Perumal G, Chatterjee S, Swayne M, Kinahan D, et al. Advances in laser-based surface texturing for developing antifouling surfaces: A comprehensive review. *Applied Surface Science Advances* [Internet]. 2023 Dec 1 [cited 2025 Jul 22];18:100513. Available from: <https://www.sciencedirect.com/science/article/pii/S2666523923001472?via%3Dihub>
- [28] 28. Bloecher N, Solvang T, Floerl O. Efficacy testing of novel antifouling systems for marine sensors. *Ocean Engineering* [Internet]. 2021 Nov 15 [cited 2025 Jul 22];240:109983. Available from: <https://www.sciencedirect.com/science/article/pii/S0029801821013238?via%3Dihub>
- [29] 29. Richards C, Slaimi A, O'connor NE, Barrett A, Kwiatkowska S, Regan F. Bio-inspired Surface Texture Modification as a Viable Feature of Future Aquatic Antifouling Strategies: A Review. *International Journal of Molecular Sciences* 2020, Vol 21, Page 5063 [Internet]. 2020 Jul 17 [cited 2025 Jul 22];21(14):5063. Available from: <https://www.mdpi.com/1422-0067/21/14/5063/htm>
- [30] 30. Murosaki T, Ahmed N, Gong JP. Antifouling properties of hydrogels. *Sci Technol Adv Mater* [Internet]. 2011 Dec [cited 2025 Jul 23];12(6):064706. Available from: <https://www.tandfonline.com/doi/pdf/10.1088/1468-6996/12/6/064706>
- [31] 31. Soliman YAA, Brahim AM, Moustafa AH, Hamed MAF. Antifouling evaluation of extracts from Red Sea soft corals against primary biofilm and biofouling. *Asian Pac J Trop Biomed* [Internet]. 2017 Nov 1 [cited 2025 Jul 22];7(11):991–7. Available from: <https://www.sciencedirect.com/science/article/pii/S2221169117310286?via%3Dihub>
- [32] 32. Chen J De, Yi RZ, Sun CL, Feng DQ, Lin YM. Antifouling Activity of Simple Synthetic Diterpenoids against Larvae of the Barnacle *Balanus albicostatus* Pilsbry. *Molecules* 2010, Vol 15, Pages 8072-8081 [Internet]. 2010 Nov 9 [cited 2025 Jul 22];15(11):8072–81. Available from: <https://www.mdpi.com/1420-3049/15/11/8072/htm>